

AD-A128 690

X-RAY TOPOGRAPHY OF HYDRIDE DOMAINS(U) ILLINOIS UNIV AT  
URBANA MATERIALS RESEARCH LAB S R STOCK ET AL. APR 83  
N00014-75-C-1012

1/1


UNCLASSIFIED

F/G 7/4

NL



END  
DATE  
FILMED  
6-83  
DTIC

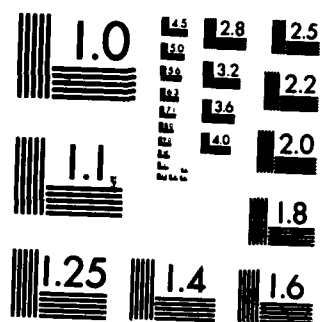

MICROCOPY RESOLUTION TEST CHART  
NATIONAL BUREAU OF STANDARDS-1963-A

Unclassified  
Security Classification

AD A 128 690

10

DOCUA

(Security classification of title, body of abstract and indexing annotation must be entered when the overall report is classified)

1. ORIGINATING ACTIVITY (Corporate author)

Department of Metallurgy and Mining Eng.  
University of Illinois at Urbana-Champaign

2a. REPORT SECURITY CLASSIFICATION

Unclassified

2b. GROUP

3. REPORT TITLE

X-ray Topography of Hydride Domains

4. DESCRIPTIVE NOTES (Type of report and inclusive dates)

Technical Report April 1983

5. AUTHOR(S) (Last name, first name, initial)

Stock, S.R., Chasnov, R, Chen, H and Birnbaum, H.K.

6. REPORT DATE

April 1983

7a. TOTAL NO. OF PAGES

8

7b. NO. OF REFS

6

8a. CONTRACT OR GRANT NO.

USN 00014-75-C-1012

a. PROJECT NO.

c.

d.

9a. ORIGINATOR'S REPORT NUMBER(S)

9b. OTHER REPORT NO(S) (Any other numbers that may be assigned this report)

10. AVAILABILITY/LIMITATION NOTICES

**DISTRIBUTION STATEMENT A**

Approved for public release;  
Distribution Unlimited

11. SUPPLEMENTARY NOTES

12. SPONSORING MILITARY ACTIVITY

Office of Naval Research

13. ABSTRACT

X-ray topographic techniques were applied to the study of twin related domains in niobium hydride and deuteride crystals. It was shown that contrast between the domains results from the small differences in orientation. The procedure has the advantages of not requiring as careful surface preparation as required by optical methods and of being a relatively rapid technique. The method can be applied to any of the single crystal hydrides.

DTIC FILE COPY

DTIC  
ELECTE  
MAY 27 1983  
D

DD FORM 1 JAN 64 1473

Unclassified  
Security Classification

88 05 12 018

UNCLASSIFIED

Security Classification

14 KEY WORDS	LINK A		LINK B		LINK C	
	ROLE	WT	ROLE	WT	ROLE	WT
Hydrides Niobium hydride X-ray topography Domain boundaries Twins						

## INSTRUCTIONS

1. **ORIGINATING ACTIVITY:** Enter the name and address of the contractor, subcontractor, grantee, Department of Defense activity or other organization (*corporate author*) issuing the report.

2a. **REPORT SECURITY CLASSIFICATION:** Enter the overall security classification of the report. Indicate whether "Restricted Data" is included. Marking is to be in accordance with appropriate security regulations.

2b. **GROUP:** Automatic downgrading is specified in DoD Directive 5200.10 and Armed Forces Industrial Manual. Enter the group number. Also, when applicable, show that optional markings have been used for Group 3 and Group 4 as authorized.

3. **REPORT TITLE:** Enter the complete report title in all capital letters. Titles in all cases should be unclassified. If a meaningful title cannot be selected without classification, show title classification in all capitals in parenthesis immediately following the title.

4. **DESCRIPTIVE NOTES:** If appropriate, enter the type of report, e.g., interim, progress, summary, annual, or final. Give the inclusive dates when a specific reporting period is covered.

5. **AUTHOR(S):** Enter the name(s) of author(s) as shown on or in the report. Enter last name, first name, middle initial. If military, show rank and branch of service. The name of the principal author is an absolute minimum requirement.

6. **REPORT DATE:** Enter the date of the report as day, month, year, or month, year. If more than one date appears on the report, use date of publication.

7a. **TOTAL NUMBER OF PAGES:** The total page count should follow normal pagination procedures, i.e., enter the number of pages containing information.

7b. **NUMBER OF REFERENCES:** Enter the total number of references cited in the report.

8a. **CONTRACT OR GRANT NUMBER:** If appropriate, enter the applicable number of the contract or grant under which the report was written.

8b, 8c, & 8d. **PROJECT NUMBER:** Enter the appropriate military department identification, such as project number, subproject number, system numbers, task number, etc.

9a. **ORIGINATOR'S REPORT NUMBER(S):** Enter the official report number by which the document will be identified and controlled by the originating activity. This number must be unique to this report.

9b. **OTHER REPORT NUMBER(S):** If the report has been assigned any other report numbers (either by the originator or by the sponsor), also enter this number(s).

10. **AVAILABILITY/LIMITATION NOTICES:** Enter any limitations on further dissemination of the report, other than those

imposed by security classification, using standard statements such as:

- (1) "Qualified requesters may obtain copies of this report from DDC."
- (2) "Foreign announcement and dissemination of this report by DDC is not authorized."
- (3) "U. S. Government agencies may obtain copies of this report directly from DDC. Other qualified DDC users shall request through \_\_\_\_\_."
- (4) "U. S. military agencies may obtain copies of this report directly from DDC. Other qualified users shall request through \_\_\_\_\_."
- (5) "All distribution of this report is controlled. Qualified DDC users shall request through \_\_\_\_\_."

If the report has been furnished to the Office of Technical Services, Department of Commerce, for sale to the public, indicate this fact and enter the price, if known.

11. **SUPPLEMENTARY NOTES:** Use for additional explanatory notes.

12. **SPONSORING MILITARY ACTIVITY:** Enter the name of the departmental project office or laboratory sponsoring (paying for) the research and development. Include address.

13. **ABSTRACT:** Enter an abstract giving a brief and factual summary of the document indicative of the report, even though it may also appear elsewhere in the body of the technical report. If additional space is required, a continuation sheet shall be attached.

It is highly desirable that the abstract of classified reports be unclassified. Each paragraph of the abstract shall end with an indication of the military security classification of the information in the paragraph, represented as (TS), (S), (C), or (U).

There is no limitation on the length of the abstract. However, the suggested length is from 150 to 225 words.

14. **KEY WORDS:** Key words are technically meaningful terms or short phrases that characterize a report and may be used as index entries for cataloging the report. Key words must be selected so that no security classification is required. Identifiers, such as equipment model designation, trade name, military project code name, geographic location, may be used as key words but will be followed by an indication of technical context. The assignment of links, rules, and weights is optional.

Unclassified

Security Classification

TECHNICAL REPORT

OFFICE OF NAVAL RESEARCH

Contract USN 00014-75-C-1012

X-Ray Topography of Hydride Domains

by

S.R. Stock\*, R. Chasnov, H. Chen and H.K. Birnbaum

Department of Metallurgy and Mining Engineering and Materials  
Research Laboratory, University of Illinois at Urbana-Champaign  
Urbana, Illinois 61801 USA

April 1983

Accession For	
NTIS GRA&I	<input checked="checked" type="checkbox"/>
DTIC TAB	<input type="checkbox"/>
Unannounced	<input type="checkbox"/>
Justification	
By <u>Pex Ltr. on File</u>	
Distribution/	
Availability Codes	
Dist	Avail and/or Special
A	



**DISTRIBUTION STATEMENT A**

Approved for public release;  
Distribution Unlimited

\*Presently at: Department of Materials Science and Engineering and Materials  
Research Center, Northwestern University, Evanston, Illinois 60201 USA

THIS DOCUMENT IS UNCLASSIFIED. DISTRIBUTION AND REPRODUCTION IS PERMITTED FOR ANY  
PURPOSE OF THE U.S. GOVERNMENT

## ABSTRACT

X-ray topographic techniques were applied to the study of twin related domains in niobium hydride and deuteride crystals. It was shown that contrast between the domains results from the small differences in orientation. The procedure has the advantages of not requiring as careful surface preparation as required by optical methods and of being a relatively rapid technique. The method can be applied to any of the single crystal hydrides.

## 1. INTRODUCTION

The attention focused on metal-hydrogen systems in recent years has resulted in the development of a number of techniques for examining the structure and morphology of the hydride phases (Schober and Linke 1976a). The orthorhombic  $\beta$ -NbH phase has been shown to consist of six twin-related orientations of the hydride which derive from the ordering of the hydrogen interstitials in the original b.c.c. structure. Schober and Linke (1976b) and Birnbaum et al (1976) have used optical microscopy with polarized light to reveal the inter-relationship between differently oriented domains of the hydride phase and the domain structure has also been examined with TEM (Schober 1975). Based on these observations, it appears that arrays of narrow twin-related domains are energetically more favorable than large blocks of a single orientation. While both the optical metallography and TEM have proven to be useful techniques to elucidate the hydride structures, they require extensive specimen preparation prior to viewing the domains.

## 2. EXPERIMENTAL

The present work describes the use of x-ray diffraction topography to image domains in  $\beta$ -NbH and  $\beta$ -NbD crystals. Relatively little surface preparation was required, aside from an ordinary metallographic polish. The

time required to produce a topograph on dental film with a double crystal camera and with radiation from a conventional sealed tube source was less than one hour.

Niobium crystals grown by a strain-anneal technique were spark machined to produce (110) surfaces which were then mechanically polished. Hydride and deuteride crystals having the compositions  $\text{NbH}_{0.78}$  and  $\text{NbD}_{0.75}$  were grown by slow cooling of the niobium crystal from 700°C under controlled pressures of hydrogen and deuterium gases, respectively. X-ray topographs were taken of the niobium-hydride (deuteride) crystals using asymmetric crystal topography (ACT), a variant of double crystal topography (Boettinger *et al* 1976), in the non-dispersive Bragg configuration. Sealed tube x-ray sources having spot focuses were used to provide the characteristic  $\text{Mo K}_\alpha$  or  $\text{Cu K}_\alpha$  radiation. The  $g = [220]$  diffraction vector was used for the reflection topographs which were recorded on Ilford L4, 50  $\mu\text{m}$  thick nuclear emulsions, or on Kodak double sided DF-57 dental film. The former provides much better resolution whereas the latter requires considerably less exposure for adequate contrast (exposures of about 45 minutes were required using  $\text{Mo K}_\alpha$  radiation produced at 45 kV with a tube current of 20 mA).

### 3. RESULTS AND DISCUSSION

Back reflection Laue photographs of the  $\text{NbH}_{0.78}$  and  $\text{NbD}_{0.75}$  crystals showed splitting of the diffraction spots which was not present before the introduction of hydrogen or deuterium and which indicates the formation of a domain structure within the crystals. The spatial arrangement of domains in a deuteride crystal is seen in the optical micrograph of the  $\text{NbD}_{0.75}$  crystal (Fig. 1a) and in the corresponding reflection topographs (Figs. 1b and c). As shown by the optical micrograph (Fig. 1a), which was taken with oblique illumination, the structure of the hydride crystal consists of sets of domains

arranged in a plate morphology. Each region, such as those marked A - F, contains at least two sets of domains. This structure has been shown (Schober 1975, Schober and Linke 1976a and b, Schober and Wenzl 1976, Birnbaum et al 1976), to consist of sets of parallel, twin related domains or regions where H ordering on subsets of interstitial sites has produced elastic distortions of the cubic structure such that the resulting orthorhombic structures are twin related. In the optical micrographs the contrast is due to the surface tilts associated with the twinning. (Similar contrast may be obtained using polarized light and results from the optical anisotropy of the orthorhombic structure).

Domain structures, identical to those seen in the optical micrographs, were obtained using reflection topography as shown in Figs. 1b and 1c. In this case the contrast is due to the variation of the diffraction conditions between the different domains. A rotation of the specimen crystal by a fraction of a degree resulted in a redistribution of diffracted intensity as may be seen by comparing topographs shown in Figs. 1b and 1c. The twin related domains within regions such as A were oriented for diffraction in Fig. 1b but not in Fig. 1c while the reverse was true for the domains in regions such as F. All regions of the crystal could be brought into a diffraction condition by varying the orientation of the crystal. The observed contrast cannot be caused by surface irregularities or topology as it is extremely sensitive to the crystal orientation. The contrast and its dependence on the orientation of the crystal was consistent with the crystallography of the twin related domains (Schober and Wenzl 1976) which form on hydrogen ordering from the  $\alpha'$  solid solution to form the  $\beta$  hydride phase. Minor differences between the optical micro-graphs and the topographs were due to the depth of penetration of the x-rays and the resulting observation of the domain structures beneath the surface of the crystal.



An example of the domain structure in a hydride crystal of composition  $\text{NbH}_{0.78}$  is given in Fig. 2. This topograph, taken with  $\text{Mo K}_\alpha$  radiation, diffraction vector  $\underline{g} = [220]$  and an L4 emulsion shows finer details than are visible in the topographs recorded on the DF-57 emulsions. Optical microscopy with oblique lighting and with polarized illumination was unsuccessful in revealing the domain structure due to relatively poor surface preparation. Nevertheless, the absorption depth of the  $\text{Mo K}_\alpha$  radiation was sufficiently large to minimize the effect of surface damage and allow the domains to be imaged.

Two types of boundaries between neighboring domains were evident in the topographs of the  $\text{NbH}_{0.78}$  and  $\text{NbD}_{0.75}$  crystals. As discussed by Schober and Linke (1976b), the straight boundaries correspond to coherent twin boundaries between hydride (deuteride) domains, and the irregular boundaries correspond to incoherent twin boundaries. Trace analysis of the coherent boundaries revealed by x-ray topography is consistent with the interface planes identified by Schober and Linke (1976b):  $\{100\}_c$ ,  $\{110\}_c$ ,  $\{111\}_c$ ,  $\{210\}_c$  and  $\{211\}_c$ .

As indicated by observations similar to those discussed above, x-ray diffraction topography provides a practical alternative to optical metallography for the study of hydride domain structures. This technique has the advantages of requiring minimal surface preparation and of being a relatively rapid procedure.

#### ACKNOWLEDGEMENTS

This work was supported by the Office of Naval Research through contract N00014-75-C-1012. We would also like to acknowledge use of the facilities of the MRL Center for Microanalysis of Materials which is supported as a national facility by the Materials Sciences Division of the Department of Energy.


## REFERENCES

- Birnbaum, H.K., Grossbeck, M.L. and Amano, M. (1976). J. Less-Common Met., 49, 357-370.
- Boettinger, W.J., Burdette, H.E., Kwiya, M. and Green, R.E., Jr. (1976). Rev. Sci. Instrum., 47, 906-911.
- Schober, T. (1975). Phys. Stat. Sol. (a), 29, 395-406.
- Schober, T. and Linke, U. (1976a). Metallography, 9, 309-320.
- Schober, T. and Linke, U. (1976b). J. Less-Common Met., 49, 63-86.
- Schober, T. and Wenzl, H. (1976). Phys. Stat. Sol. (a), 33, 673-681.


## FIGURE CAPTIONS

Figure 1. Optical micrograph and corresponding ACT x-ray topographs showing the domain structure in a  $\text{NbD}_{0.75}$  crystal. Fig. 1a is the optical micrograph taken with oblique illumination. Figs. 1b and 1c are x-ray topographs with the crystal in different orientations to bring different domains into a diffracting orientation. The images were recorded using  $\text{Cu K}_\alpha$  radiation and  $g = [220]$  on double sided Kodak DF-57 film. The double sided film resulted in a loss of resolution but allowed images to be recorded in 45 minutes. The magnification for all images is as indicated on Fig. 1c.

Figure 2. ACT topograph of a  $\text{NbH}_{0.78}$  crystal taken with  $\text{Mo K}_\alpha$  radiation and  $g = [220]$ . The image was recorded on Ilford L4, 50  $\mu\text{m}$  thick emulsion which improved the resolution as compared to the results obtained with the double sided film (Figs. 1b and c).

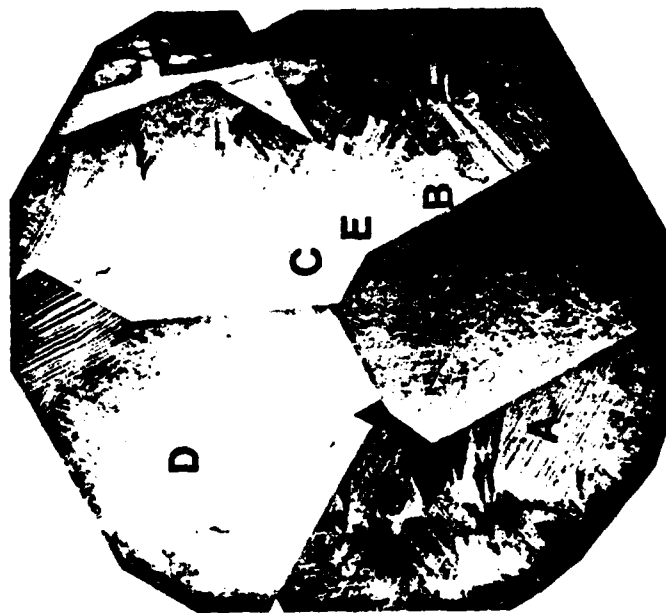

**a**

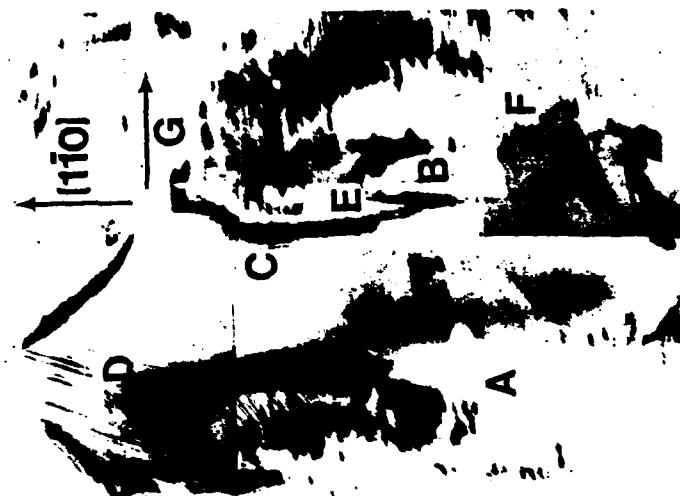


**b**



**c**

Fig. 1  
Stock et al

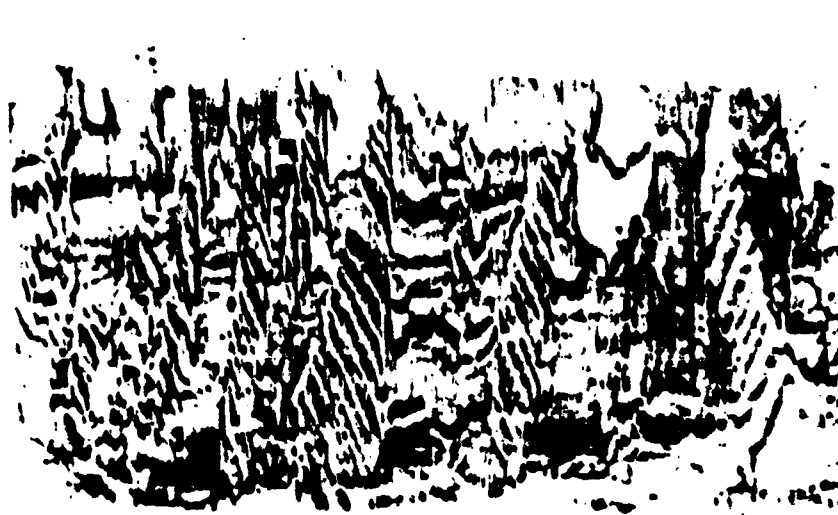

$[1\bar{1}0]$

1 mm

Fig 2  
Stock et al

